

FORMULATION OF RELATIONSHIP BETWEEN VISCOSITY AND TEMPERATURE FOR PALM KERNEL OIL BIODIESEL

*¹Alamu O. J., ¹Oyelami S. ²Adebisi S. A. and ³Babatunde K. A.

¹Department of Mechanical Engineering, Osun State University, P.M.B. 4494, Osogbo, Nigeria.

²Department of Chemical Sciences, Osun State University, P.M.B. 4494, Osogbo, Nigeria.

³Department of Chemical Engineering, Ladoké Akintola University of Technology, Ogbomoso, Nigeria.

Article Received on 28/03/2019

Article Revised on 18/04/2019

Article Accepted on 08/05/2019

*Corresponding Author

Alamu O. J.

Department of Mechanical Engineering, Osun State University, P.M.B. 4494, Osogbo, Nigeria.

ABSTRACT

Production of Biodiesel from Palm kernel oil (PKO) through transesterification with ethanol using potassium hydroxide (KOH) catalyst was accomplished in a previous study. Characterization of the PKO biodiesel was undertaken. From the results, a possible relationship between viscosity and the temperature of the PKO

biodiesel was obtained using the least square regression approach. The resulting Viscosity–

Temperature model $\mu_{PKO\text{biodiesel}} = 6.4592e^{-0.0075T}$ was developed into a computer program and run with a compiler using lower bound temperature (0°C), below the pour point of the PKO biodiesel; upper bound temperature (325°C), above the flash point as well as boiling point of the PKO biodiesel and temperature incremental step of 0.2°C. The computer program generated a database for prediction of viscosity of PKO biodiesel at varying temperatures, with minimal error. Results obtained are in good agreement with experimental measurements.

KEYWORDS: Biodiesel, Palm kernel oil, viscosity, Temperature.

INTRODUCTION

It has been widely reported that the depletion of world petroleum reserves, harmful exhaust emissions from engines, instability in the prices of petroleum products and uncertainties of their supply have created renewed interest among researchers to search for suitable alternative fuels. Greener fuels sources are now attracting wide societal and political interests, especially for its reduced greenhouse emissions, biodegradability and sustainability (Anwar *et al.*, 2010; Baroutian *et al.*, 2011; Agbede *et al.*, 2012; Hayyan *et al.*, 2013; Sakthivel *et al.*, 2014; Elkady *et al.*, 2015). Possible substitutes to fossil fuels are oils extracted from animal or vegetable sources.

Biodiesel, produced mostly through transesterification of vegetable oils and animal fats, offers one of the most promising solutions to the ever-increasing demand of diesel.

Several feedstocks have been considered for production of biodiesel in different parts of the world. There are reports on efforts of researchers on Canola in Canada, China, India, France, Austria and Germany (as reported in Marchetti, 2009); Corn in USA, Mexico, Russia and the United Kingdom (Nisa and Hamzah, 2012; Anastopoulus *et al.*, 2013; Alhassan *et al.*, 2014); Soybean in USA, Argentina, Brazil, India and China (Kim *et al.*, 2010; Gomes *et al.*, 2011; Pisarello *et al.*, 2014); Sunflower in Russia, Argentina, France, Italy and Germany (Sankaranarayanan, 2012; Saba *et al.*, 2016); Coconut in Malaysia, Vietnam, Mozambique, Bangladesh and Ghana (Sulaiman *et al.*, 2010; Hossain *et al.*, 2012); *Jatropha curcas* in India, Yemen and Nigeria (Baggash and Abdulrahman, 2010; Umaru and Aberuagba, 2012) and Palm oil as well as Palm kernel oil in Malaysia, Indonesia, China, Mexico, Colombia, Cote d'Ivoire, Ghana and Nigeria (Alamu *et al.*, 2007,2009; Suppalakpanya *et al.*, 2010; Baroutian *et al.*, 2012; Shahla *et al.*, 2012; Lee and Ofori-Boateng, 2013; Noipin and Kumar, 2014; Wong *et al.*, 2015).

Alamu *et al.* (2007, 2009) used Nigerian Palm kernel oil as feedstock and KOH as catalyst for transesterification of PKO with ethanol to obtain PKO biodiesel. Fuels, including biodiesel, are generally characterized through tests for properties such as specific gravity, viscosity, pour point and cloud point amongst others.

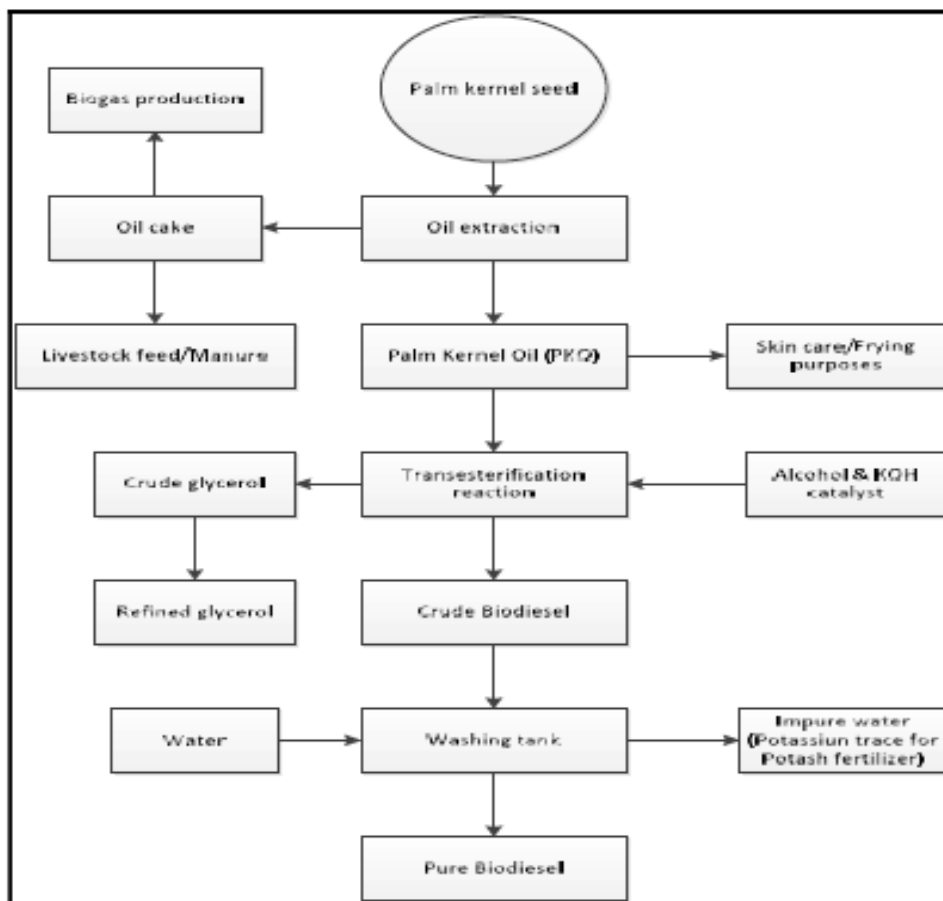


Fig. 1: Process flow chart for biodiesel production from palm-kernel Oil.

Alamu *et al.* (2007, 2009) analyzed the PKO biodiesel and the commercial grade fossil diesel for basic fuel properties such as specific gravity at reference 60^oF, viscosity at 40^oC, pour point, cloud point and flash point following ASTM standard test procedures. Specific gravity and viscosity measurements were made using the Thermal-Hydrometer apparatus and Viscometer, following ASTM standards D1298 and D445 respectively. Results obtained are re-presented in Table 1.

Viscosity, the measurement of the internal flow resistance of a liquid, constitutes an intrinsic property of vegetable oils. It is of remarkable influence in the mechanism of atomization of the fuel being injected into the engine combustion chamber. Viscosity of liquid fuel has been reported to vary with temperature (Krisnangkura *et al.*, 2005). This work therefore seeks to establish possible empirical relationship between viscosity and temperature for palm kernel oil (PKO) biodiesel, which had previously been produced through transesterification of PKO with ethanol using potassium hydroxide (KOH) catalyst.

MATERIALS AND METHOD

The PKO Biodiesel Fuel

The PKO biodiesel used was produced through transesterification process depicted in Fig.1 using 100g PKO, 20.0% ethanol (wt% PKO), 1.0% KOH catalyst at 60°C reaction temperature and 90 min. reaction time. The transesterification process yielded 95.4% PKO biodiesel. The biodiesel was characterized as alternative diesel fuel through series of ASTM standard fuel tests. The PKO biodiesel had 85.06% reduction of viscosity over its raw vegetable oil at 40°C, while its pour point, flash point and boiling point were 2oC, 167°C and 320°C respectively (Alamu et al., 2007; 2009).

Table 1: Measured PKO biodiesel and fossil diesel fuel properties.

Fuel Characteristics (Properties)	Values (PKO biodiesel)	(Petroleum diesel)
Pour point (oC)	2	-16
Cloud point (oC)	6	-12
Flash Point (oC)	167	74
Boiling Point (oC)	320	191
Gross heat of combustion (MJ/kg)	40.56	45.43
Net heat of combustion (MJ/kg)	37.25	42.91
Specific gravity (at 15.56oC)	0.883	0.853
Viscosity (at 40oC) (mm ² /s)	4.839	2.847

Test for Viscosity

Amongst series of tests conducted in characterizing the PKO biodiesel produced as fuel, viscosity measurements were made following ASTM D445 standard test procedure. Viscosity of the Biodiesel produced were measured (in centistokes (cSt)) using viscometer (Canon-Fenske Calibrated, 15cSt max. range), between the temperature intervals of 10⁰C and 60⁰C. Similar measurements were made for commercial grade petroleum diesel, for comparison (Alamu et al., 2007; 2009).

Viscosity-Temperature correlation for PKO biodiesel

Several methods of correlating viscosities of different petroleum fractions with temperature have been reported. The Andrade equation, which correlates liquid viscosity and temperature is of the form:

$$\mu = Ae^{\frac{B}{T}} \dots\dots\dots (1)$$

Where A and B are constants, T is absolute temperature.

Equation (1) can be used for predicting viscosity up to approximately the normal boiling point of the liquid. Comparing equation (1) to the reaction rate, an equation (Equation (2)) has been proposed by Eyring; as reported in Krisnangura *et al.* (2005).

$$\mu = \frac{N_A h}{V} e^{\frac{-\Delta G_{vis}}{RT}} \dots\dots\dots (2)$$

Where N_A , V , h and R are Avogadro's number, molecular volume, Plank's and gas constants, Respectively. ΔG_{vis} is the free energy of activation for flow.

Several modifications of Equation (1) have been made to extend the temperature range. Makhija and Stairs were reported in Krisnangura *et al.* (2005) to have modified Equation (1), for associated liquids, by adding a third variable parameter as shown in Equation (3).

$$\ln \mu = m + \frac{B}{T - T_0} \dots\dots\dots (3)$$

where m , B and T_0 are constants.

The effect of temperature on specific gravity of PKO biodiesel had been proposed by Alamu (2012) as shown in Equation (4).

$$SG_{EEPKO} = -0.0007T + 0.8939 \dots\dots\dots (4)$$

Where; SG_{EEPKO} = specific gravity of PKO biodiesel, T = temperature ($^{\circ}C$).

In this work, the relationship between viscosity and temperature for both the PKO biodiesel and the petroleum diesel was formulated using the Andrade model.

The constants A and B in equation (1) were determined through linear least square regression method to obtain a model for calculation of viscosity of each fuel at various temperatures, inclusive of ranges not covered by the experimental measurements. This was achieved with the aid of simple computer codes developed in Visual Basic. The software generates viscosity for intended temperature range (within practical limitations) and specific temperature incremental step of interest, as a notepad file on the hard drive of the computer.

Using the developed model (equation 6), the viscosity of the PKO biodiesel was computed at different temperatures. The program was run with a Visual Basic 6.0 professional edition compiler using lower bound temperature (0°C), below the pour point (2°C); and upper bound temperature (325°C), above the flash (167°C) and boiling (320°C) point of the PKO biodiesel. Temperature incremental step of 0.2°C was used (Figure 2).

RESULTS AND DISCUSSION

Viscosity of PKO Biodiesel Fuel

It was noted from previous results that esterification of PKO produced a marked decrease in values of viscosity from the reported range 30-50 mm²/s for vegetable oils at 40°C to 4.839mm²/s for PKO biodiesel at the same temperature. With this value of viscosity, it implies that a reduction of about 85% viscosity has been achieved in the PKO fuel. This reduction in viscosity will enhance the fluidity of the PKO biodiesel in diesel engine.

However, from Table 1, PKO biodiesel has higher viscosity than conventional diesel fuel in agreement with reports from several researchers who conducted similar investigation on the same feedstock after results from Alamu *et al.* (2007) appeared in print (Kuwornoo and Ahiekpor, 2010; Nisa and Hamzah, 2012; Igbokwe and Obiukwu, 2013; Bejan *et al.*, 2014; Igbokwe and Nwafor, 2016). The PKO biodiesel viscosity of 4.839 mm²/s obtained at 40°C reference temperature is almost twice the viscosity of the fossil diesel as found also in alcohol esters of rapeseed, canola, beef tallow and soybean (Kim *et al.*, 2010; Gomes *et al.*, 2011; Aworanti *et al.*, 2012; Pisarello *et al.*, 2014; Rajaeifa *et al.*, 2014). The value also falls within the specified limits by ASTM D6751, ASTM D975 and BIS (India) standards.

Table 2: Viscosity values obtained for PKO biodiesel and petroleum biodiesel.

Temperature (°C)	Viscosity of fuel samples in cSt		
	(PKO biodiesel)	(Petroleum diesel)	□PKO biodiesel Petroleum diesel
10.0	5.979	3.540	1.689
15.0	5.727	3.401	1.684
20.0	5.556	3.270	1.699
25.0	5.330	3.151	1.692
30.0	5.188	3.050	1.701
35.0	5.000	2.920	1.712
40.0	4.839	2.847	1.700
45.0	4.607	2.710	1.700
50.0	4.425	2.612	1.694
55.0	4.265	2.510	1.699

60.0	4.078	2.421	1.684
------	-------	-------	-------

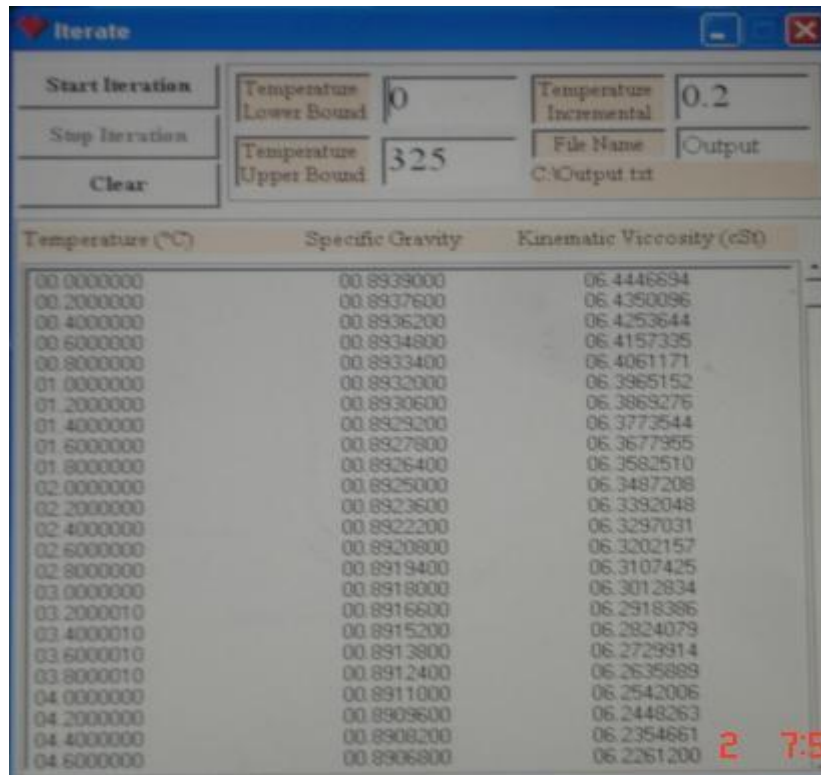


Fig. 2: The software window after compilation.

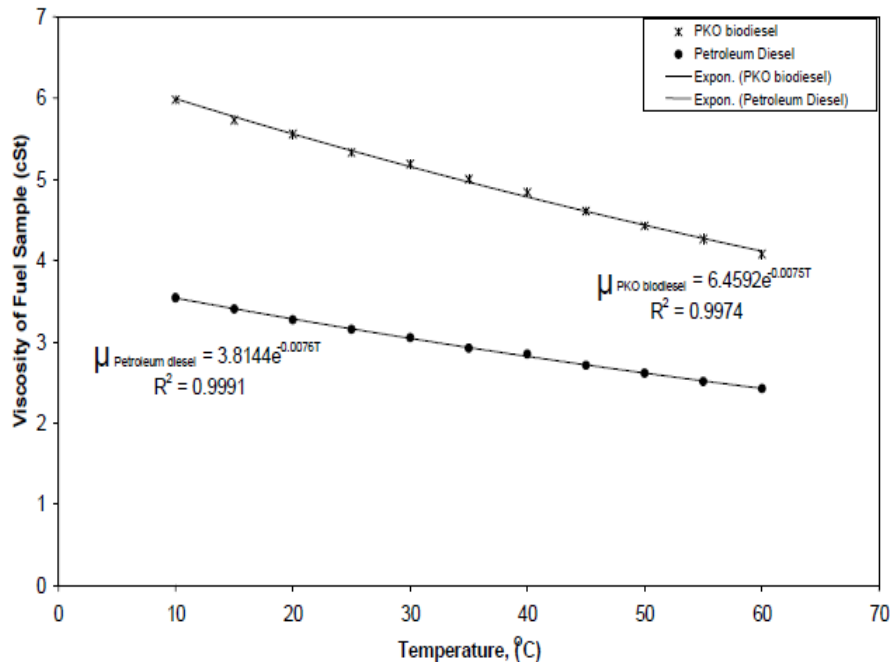


Fig. 3: Variation of Viscosity with Temperature for PKO biodiesel and Petroleum Diesel Viscosity (cSt).

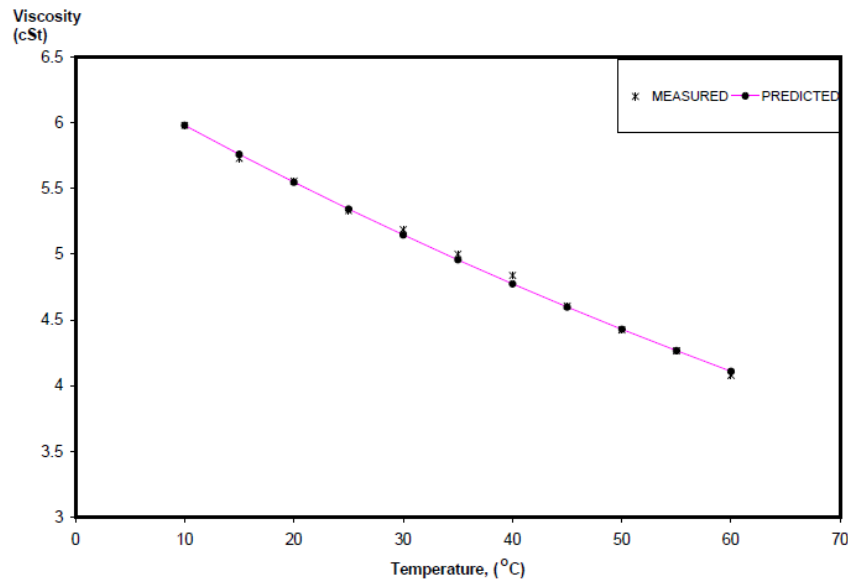


Fig. 4: Comparison between measured and predicted variation of viscosity with temperature for PKO biodiesel.

As presented in Table 2, the ratio of viscosity of PKO biodiesel to that of petroleum diesel at the same temperature ranges between 1.684 and 1.712. This shows that PKO biodiesel is almost twice as viscous as conventional petroleum derived diesel.

Viscosity-Temperature Correlation for PKO Biodiesel

From Table 2, evident from Fig.3, using the linear least square regression method, a linear regression equation is developed as:

$$\mu_{Petroleumdiesel} = 3.81e^{-0.0076T} \dots\dots\dots (5)$$

For the petroleum diesel used, and;

$$\mu_{PKObiodiesel} = 6.4592e^{-0.0075T} \dots\dots\dots (6)$$

For the Palm kernel oil biodiesel.

The R² value for the linear regression equation for the petroleum diesel (equation 5) and PKO biodiesel (equation 6) are respectively 0.9991 and 0.9974. With these values, the equations could be considered to have described the relationship between the two parameters with a fair degree of accuracy.

It is also observed that the linear regression equation for the petroleum diesel (equation 5) and PKO biodiesel (equation 6) agree very closely in form with Andrade Equation (Equation 1). Therefore, for Biodiesel, comparing equations 1 and 6, the Andrade's constants;

$$A = 6.4592 \quad \text{and}$$

$$\frac{B}{T} = -0.0007T \quad \text{or} \quad B = -0.0007T^2 \quad \dots\dots\dots (7)$$

With these expressions, viscosities of the PKO biodiesel can be computed at different temperatures.

The viscosity-temperature correlation obtained for PKO biodiesel is also observed to be in good agreement with proposition of Eyring in equation 2. Comparing equation 2 with equation 6, it can be proposed, for PKO biodiesel that:

$$\frac{N_A h}{V} = 6.4592 \quad \dots\dots\dots (8)$$

$$\frac{\Delta G_{vis}}{RT} = 0.0007T \quad \dots\dots\dots (9)$$

Comparison between Predicted and Measured Values

A comparison made between simulated results and actual experimental measurements showed reasonable agreement as there were no appreciable deviation in viscosity. Between the range (10–60°C), the maximum and minimum deviation of computed results from experimental measurements were 6.5% and 0.0%. Similarly, for specific gravity, within the same range of temperature, the maximum and minimum deviation of computed results from experimental measurements were 1.5% and 0.0% (Alamu, 2012).

It should be noted that the comparison made above may not be sufficient to conclude that the correlation agrees perfectly with experimental measurements as available data for experimental measurements in this work was limited to 60°C. However, within the available experimental data range, the predicted results from the least square regression model are in very close agreement with values obtained experimentally. This is further illustrated in Fig.4.

From Fig.4, closer agreement was observed between the computed and measured viscosity

values within the temperature range of (10-30) °C and (45-60) °C. The relatively higher deviation recorded between the measured and predicted viscosity of the PKO biodiesel occur at 40°C. Similarly, as with specific gravity, the higher deviation reported here is not greater than 6.5%. Thus, with the level of agreement between the measured and computed values of viscosity, results generated from the computer simulation can be used for prediction of specific gravity of PKO biodiesel with minimal error.

CONCLUSION

Viscosity–Temperature model was formulated for PKO biodiesel through least square regression method with R^2 value of 0.9974. The regression equation $\mu_{PKO\text{biodiesel}} = 6.4592e^{-0.0075T}$ obtained for PKO biodiesel agree very closely in form with Andrade equation, which correlate liquid viscosity and temperature. With this expression, viscosities of the PKO biodiesel can be computed at different temperatures.

REFERENCES

1. Agbede, O.O., Alade, A.O., Adebayo, G.A., Salam, K.K. and Bakare, T. Evaluation of Chosen Fruit Seeds Oils as Potential Biofuel, *International Agrophysics*, 2012; 26(2): 199-202.
2. Alamu, O.J. Development of Empirical Relationship between Specific Gravity and Temperature for Palm Kernel Oil Biodiesel, *Proc. Energy Technology and Management Conference*, University of Ibadan, Nigeria, (5th – 7th September, 2012), 2012; 319-328.
3. Alamu, O.J., Waheed, M.A. and Jekayinfa, S.O. Effect of Ethanol-Palm Kernel Oil Ratio on Alkali-Catalysed Biodiesel Yield, *Fuel - Elsevier*, 2007; 87(8-9): 1529-1533.
4. Alamu, O.J., Waheed, M.A. and Jekayinfa, S.O. Determination of Optimum Temperature for the Laboratory Preparation of Biodiesel from Nigerian Palm Kernel Oil, *Energy Sources, Part A - Taylor and Francis*, 2009; 31(13): 1105-1114.
5. Alhassan, Y., Kumar, N., Bugaje, I.M., Pali, H.S. and Kathkar, P. Co-solvents Transesterification of Cotton Seed Oil into Biodiesel: Effects of Reaction Conditions on Quality of Fatty Acids Methyl Esters, *Energy Conversion and Management*, 2014; 8: 640-648.
6. Anastopoulos, G., Dodos, G.S., Kalligeros, S. and Zannikos, F. - Biomass CaO Loaded with Sr (NO₃)₂ as a Heterogeneous Catalyst for Biodiesel Production from Cottonseed Oil and Waste Frying Oil, *Biomass Conversion and Biorefinery*, 2013; 3(3): 169-177.

7. Anwar, F., Rashid, U., Ashraf, M. and Nadeem, M. Okra (*Hibiscus esculentus*) seed oil for biodiesel production. *Applied Energy*, 2010; 87(2010): 779–785.
8. Aworanti, O.A., Agarry, S.E and Ajani, A.O. Statistical Optimization of Process Variables for Biodiesel Production from Waste Cooking Oil using Heterogeneous Base Catalyst, *British Biotechnology Journal*, 2013; 3(2): 116-132.
9. Baggash, M. and Abdulrahman, A. Production and Testing of Biodiesel Fuel from *Jatropha Curcas* (Al-Sharb) in Yemen, *International Journal of Renewable Energy*, 2010; 5(2): 47-56.
10. Baroutian, S., Aroua, M.K., Raman, A.A.A. and Sulaiman, N.M.N. A Packed Bed Membrane Reactor for Production of Biodiesel using Activated Carbon Supported Catalyst, *Bioresource Technology*, 2011; 10(2): 1095-1102.
11. Baroutian, S. Aroua, M.K. Abdul-Aziz, A.R. and Sulaiman, N.M.N. TiO₂/Al₂O₃ Membrane Reactor Equipped with a Methanol Recovery Unit to Produce Palm Oil Biodiesel, *International Journal of Energy Research*, 2012; 36(1): 120-129.
12. Bejan, C.C.C., Celante, V.G., Castro, E.V.R. and Pasa, V.M.D. Effect of Different Alcohols and Palm Kernel (Palmist) Oils on Biofuel Properties for Special Uses, *Energy Fuels*, 2014; 28(8): 5128-5135.
13. Elkady M.F., Zaatout, A. and Balbaa, O. Production of Biodiesel from Waste Vegetable Oil via KM Micro-mixer, *Petroleum & Environmental Biotechnology*, 2015; 6(3).
14. Gomes, M.C.S., Arroyo, P.A., Pereira, N.C. Biodiesel Production from Degummed Soybean Oil and Glycerol Removal using Ceramic Membrane, *Journal of Membrane Science – Elsevier*, 2011; 378(1-2): 453-461.
15. Hayyan, A., Hashim, M.A., Hayyana, M., Mjalli, F.S. and AlNashef, I.M. A Novel Ammonium Based Eutectic Solvent for the Treatment of Free Fatty Acid and Synthesis of Biodiesel Fuel, *Industrial Crops and Products*, 2013; 46: 392-398.
16. Hossain, M.A., Chowdhury, S.M., Rekhu, Y., Faraz, K.S. and Islam, M.U. Biodiesel from Coconut Oil: A Renewable Alternative Fuel for Diesel Engine, *World Academy of Science, Engineering and Technology*, 2012; 68: 1289-293.
17. Igbokwe, J.O. and Nwafor, O.M.I. Performance Characteristics of Palm Kernel Biodiesel and its Blend in a CI Engine, *International Journal of Ambient Energy - Taylor & Francis*, 2016; 37(1): 103-106.
18. Igbokwe, J.O. and Obiukwu. O.O. Performance Characteristics of a Diesel Engine Fuelled with Palm Kernel Methyl Ester and its blend with Petrodiesel, *Pacific Journal of Science and Technology*, 2013; 14(2): 75-79.

19. Kim, M., Yan, S., Salley, S.O. and Ng, K.Y.S Competitive Transesterification of Soybean Oil with mixed Methanol/Ethanol over Heterogeneous Catalysts, *Bioresource Technology* - Elsevier, 2010; 101(12): 4409-4414.
20. Krisnangkura, K, Yimsuwan, T and Pairintra, R. An Empirical Approach in Predicting Biodiesel Viscosity at Various Temperatures, Research Report, King Mongkut's University, Bangkok, Thailand; Elsevier Publishers, 2005.
21. Kuwornoo, D.K. and Ahiekpor, J.C. Optimization of Factors Affecting the Production of Biodiesel from Crude Palm Kernel Oil and Ethanol, *International Journal of Energy and Environment*, 2010; 1(4): 675-682.
22. Lee, K.T. and Ofori-Boateng, C. Production of Palm Biofuels toward Sustainable Development, *Green Energy and Technology*, Springer, 2013; 107-146.
23. Marchetti, J.M. A Summary of the Available Technologies for Biodiesel Production based on a Comparison of Different Feedstock's Properties, Process Safety and Environmental Protection, 2009; 90(3): 157-163.
24. Nisa, N.M. and Hamzah, M.H. Influence of Seed Particle Size on Extraction and Reactive Extraction for Biodiesel Production from Cotton and Palm Kernel Seeds, Proceedings, Humanities, Science and Engineering Research, 2012 IEEE Symposium (24-27 June, 2012), Kuala Lumpur, 2012; 251-254.
25. Noipin, K. and Kumar, S. Optimization of Ethyl Ester Production from Palm Oil, *Petroleum & Coal*, 2014; 56(3): 249-258.
26. Pisarello, M.L., Olalla, P.S. and Querini, C.A. Process Design for Biodiesel Production with Crude Soybean Oils: Methanol Recovery from the Reacting System, *Energy & Fuels*, 2014; 28(1): 571-577.
27. Rajaeifar, M.A., Ghobadian, B., Safa, M. and Heidari, M.D. Energy Life-cycle Assessment and CO₂ Emissions Analysis of Soybean-based Biodiesel: a Case Study, *Journal of Cleaner Production* - Elsevier, 2014; 66: 233-241.
28. Saba, T., Estephane, J., Khoury, B.E., Khoury, M.E., Khazma, M., Zakhem, H.E. and Aouad, S. Biodiesel Production from Refined Sunflower Vegetable Oil over KOH/ ZSM5 Catalysts, *Renewable Energy*, 2016; 90: 301-306.
29. Sakthivel, G., Nagaraiane, G., Ilangkumaran, M. and Gaikwad, A.B. Comparative Analysis of Performance, Emission and Combustion Parameters of Diesel Engine Fuelled with Ethyl ester of Fish Oil and its Diesel Blends, *Fuel* - Elsevier, 2014; 132: 116-124.
30. Sankaranarayanan, T.M. Transesterification and Hydroprocessing of Sunflower Oil over

- Heterogeneous Catalyst, PhD Thesis, Faculty of Science and Humanities, Anna University, Chennai, 2012.
31. Shahla, S., Ngoh, G.C. and Yusoff, R. Optimization of Base-catalyzed Ethyl Ester Production from Palm Oil, *Asia Pacific Journal of Chemical Engineering*, 2012; 7: S20-S25.
 32. Sulaiman S., Raman A.A.A. and Aroua, M.K. Coconut Waste as a Source for Biodiesel Production, *Proceeding ICBEE2010 - 2010 2nd International Conference on Chemical, Biological and Environmental Engineering*, Art No 5653534, 2010; 254-256.
 33. Suppalakpanya, K., Ratanawilai S.B. and Tongurai C. Production of Ethyl Ester from Crude Palm Oil by Two-step Reaction with Microwave, *Fuel – Elsevier*, 2010; 89(8): 2140-2144.
 34. Umaru, M. and Aberuagba, F. Characteristics of a Typical Nigerian *Jatropha Curcas* Oil Seeds for Biodiesel Production, *Research Journal of Chemical Sciences*, 2012; 2(10): 7-12.
 35. Wong, Y.C., Tan, Y.P., Taufiq-Yap, Y.H. and Ramli, I. An Optimization Study for Transesterification of Palm Oil using Response Surface Methodology (RSM), *Sains Malaysiana*, 2015; 44(2): 281-290.